


PREPARATION of DISPERSIONS

VANATURAL® Bentonite Clay, **VEEGUM**® Magnesium Aluminum Silicate and **VAN GEL**® Magnesium Aluminum Silicate products must be properly dispersed in water and hydrated to provide the desired performance properties.


The two guides to successful hydration are:

- ✓ *THE BEST DISPERSIONS ARE PREPARED IN WATER FREE OF ADDITIVES.*
- ✓ *MORE ENERGY INPUT GIVES QUICKER HYDRATION.*

Any materials present in the water when the clay is added, including preservatives, chelating agents or other minor additives, will interfere with hydration and inhibit the formation of the desired colloidal structure.

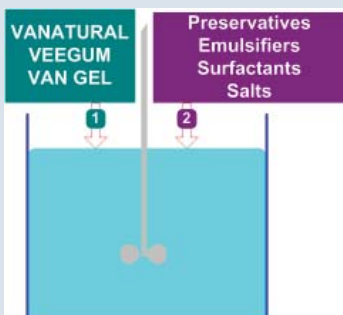


Dry clay particles are actually multiple layers of individual platelets separated by a layer of water. The extent to which these particles are delaminated into individual clay platelets is referred to as the degree of hydration. The greater the degree of hydration, the stronger the colloidal structure, and the greater the viscosity and yield value of the dispersion.

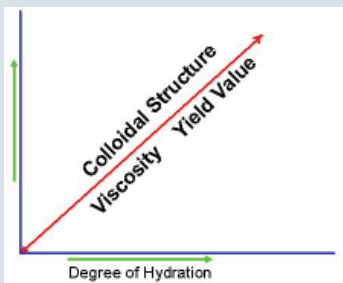


The degree of hydration is directly proportional to the amount of energy used to disperse the product, and therefore increases in proportion to the following factors:


- *Shear, or mixing intensity*
- *Heat input, or water temperature*
- *Mixing time*

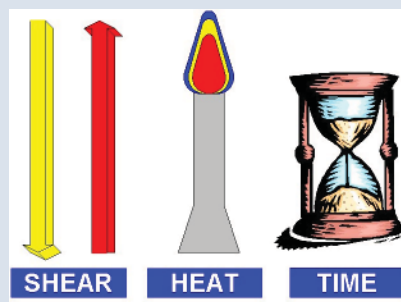

Using greater shear, or mixing for a longer time, will provide better hydration, which is measured as higher viscosity.

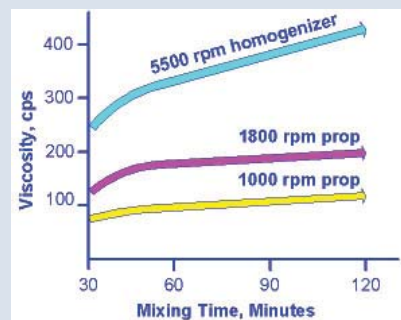

Heat input in the form of heated water has an even more pronounced beneficial effect on hydration than does the mechanical energy contribution of shear.

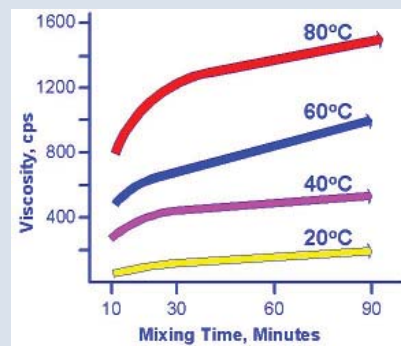

Any change in mixer intensity (e.g., speed, propeller to vessel ratio) or water temperature will affect the degree of hydration and the hydration time.

Whichever mixing conditions are used, it is very important that they be consistently controlled to achieve reproducible results in the laboratory, during scale-up and in production.

Because of its unique nature, **VEEGUM Ultra** clay is an exception. It is relatively unaffected by changes in hydration parameters. Adequate hydration of this product will be achieved in most cases in no more than 15 minutes. Increasing mixing intensity, mixing time or water temperature will not significantly affect its degree of hydration.

The table on the back provides guidelines for the minimum amounts of time suggested for the hydration of **VANATURAL**, **VEEGUM** and **VAN GEL** clays. They are based on laboratory scale preparations under practical formulating conditions. Actual hydration times in the laboratory or in production will depend on the particular combination of batch size, mixer shear and water temperature used.

In the laboratory or during production, the key to consistent performance of **VANATURAL**, **VEEGUM** and **VAN GEL** products is consistent conditions of hydration. Changes in hydration time, mixer shear, vessel size or water temperature will change results.

For detailed information on the properties and uses of these clay products, please request a copy of: "VANATURAL Bentonite, The Essential Mineral for Personal Care" and the "VEEGUM/VAN GEL" brochure.

These are also available online at:
www.rtvanderbilt.com/VANATURALTDWeb.pdf
and www.rtvanderbilt.com/veegum.pdf

R.T. Vanderbilt Company locations:

Headquarters:

R.T. Vanderbilt Company, Inc.
30 Winfield Street, P.O. Box 5150
Norwalk, CT 06856-5150
(203) 853-1400 Fax: (203) 853-1452
E-Mail: specialt@rtvanderbilt.com

West Coast Office:

6281 Beach Boulevard,
Buena Park, CA 90621
(714) 670-8084 Fax: (714) 739-1488
E-Mail: laoffice@rtvanderbilt.com

Vanderbilt International Sàrl, Headquarters:

World Trade Center II
29, route de Pré-Bois, P.O. Box 870
CH-1215 Genève 15, Switzerland
Phone: +41-(0)22-929-5734
Fax : +41-(0)22-929-5752
E-mail: Vanderbilt-Intl@rtvanderbilt.com

Vanderbilt (Beijing) Trading, Ltd.

Room 220A Tower A, No.8 Hengfeng Road
Science Town, Fengtai District, Beijing 100070,
China
Phone: 011- 86 10 58051526
Fax: 011- 86 10 58051525

www.rtvanderbilt.com



Before using, read, understand and comply with the information and precautions in the Material Safety Data Sheets, label and other product literature. The information presented herein, while not guaranteed, was prepared by technical personnel and, to the best of our knowledge and belief, is true and accurate as of the date hereof. No warranty, representation or guarantee, express or implied, is made regarding accuracy, performance, stability, reliability or use. This information is not intended to be all-inclusive, because the manner and conditions of use, handling, storage and other factors may involve other or additional safety or performance considerations. The user is responsible for determining the suitability of any material for a specific purpose and for adopting such safety precautions as may be required. R.T. Vanderbilt Company, Inc. does not warrant the results to be obtained in using any material, and disclaims all liability with respect to the use, handling or further processing of any such material. No suggestion for use is intended as, and nothing herein shall be construed as, a recommendation to infringe any existing patent, trademark or copyright or to violate any federal, state or local law or regulation.
rev10/10

VANATURAL®
Bentonite Clay

VEEGUM®
Magnesium Aluminum Silicate

VAN GEL®
Magnesium Aluminum Silicate



**PREPARATION
OF
DISPERSIONS**

Minimum Suggested Hydration Times	Normal Hydrating Grades	Quick Hydrating Grades	Ultra Hydrating Grade
Propeller Mixer: 800 rpm, 25° C water 800 rpm, 75° C water	VEEGUM® VEEGUM F VEEGUM K VEEGUM HV VEEGUM Pure VEEGUM PRO VEEGUM T VAN GEL® B VAN GEL C	VANATURAL® VEEGUM HS VEEGUM D VEEGUM Plus VAN GEL O VAN GEL ES	VEEGUM Ultra
Homogenizer: 3000 rpm, 25° C water 3000 rpm, 75° C water	120 Minutes 45 Minutes	30 Minutes 20 Minutes	15 Minutes 10 Minutes

Please contact Vanderbilt for additional information on the products listed in this brochure.

Samples and technical information are available on request.

For a complete listing of Vanderbilt products, please visit:

www.rtvanderbilt.com

VANATURAL, **VEEGUM** and **VAN GEL** are registered trademarks of R.T. Vanderbilt Company, Inc.